

DATA SHEET

CPM® REX® 76® HS (AISI M48)

Typical Composition							
C	Mn	Si	Cr	W	Mo	V	Co
1.50	0.30	0.30	3.75	9.75	5.25	3.10	8.50

CPM® REX® 76® (HS) is a super high speed steel made by the CPM® (Crucible® Particle Metallurgy) Process. It is heat treatable to HRC 68-70. Its high carbon, vanadium and cobalt contents provide abrasion resistance comparable to that of T15 and red hardness superior to that of M42. With its high hardness, fine grain size and uniform carbide distribution, CPM® Rex® 76® is an outstanding choice for special purpose cutting tools requiring high red hardness, high abrasion resistance, and good toughness.


The CPM® process results in a homogeneous microstructure with a finer, more uniform carbide distribution imparting superior dimensional stability, grindability and toughness when compared to steels produced by conventional processes. The CPM® process also allows the design of more highly alloyed grades which cannot be produced by conventional steelmaking.

The *typical applications* of CPM® Rex® 76® are End Mills, Form Tools, Shaper Cutters, Gear Nobs, Broaches, Spade Drills, Tool Bits, Milling Cutters, and Special Taps.

Note: These are some typical applications. Your specific application should not be undertaken without independent study and evaluation for suitability.



CPM® STEEL

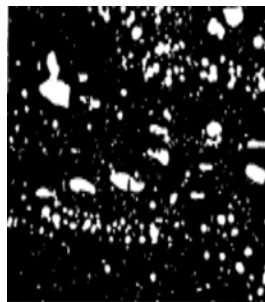

CONVENTIONAL STEEL

Machinability in the annealed condition is approximately 15% of W1 Tool Steel (1%C).

Grind ability of CPM® Rex® 76® compares favorably with regular high speed steels because of the fine, uniformly distributed carbides. Conventional grinding wheels designed for high speed steels can be used. In special cases, the advice of a grinding wheel manufacturer should be sought.

Surface Treatments

CPM® Rex® 76® can be nitrided or PVD coated if desired. If a CVD treatment is used, subsequent hardening is required and may result in undesirable distortion.

This data sheet is for informational purposes only. Alloy characteristics are subject to change due to chemical composition and/or processing. We do not certify the material's suitability for specific applications.



DATA SHEET

Thermal Treatments

Critical Temperature: 1535°F (835°C) .

Forging: 2000-2100°F (1095-1150°C). Do not forge below 1700°F (925°C). Slow cool after forging.

Annealing

Heat to 1600°F (870°C), hold 2 hours, slow cool no faster than 25°F (15°C) per hour to 1000°F (540°C), then furnace cool or cool in still air to room temperature.

Annealed Hardness: Approx. BHN 285/311

Stress Relieving

Annealed parts: Heat to 1100-1300°F (595-705°C), hold 2 hours, then furnace cool or cool in still air.

Hardened parts: Heat to 25°F (15°C) below original tempering temperature, or 1000°F (540°C) minimum, hold 2 hours, then furnace cool or cool in still air.

Hardening (Salt or High Pressure Vacuum preferred)

Pre-heat: Heat to 1500-1550°F (815-845°C), hold long enough to soak through. For vacuum heat treating, an additional pre-heat at 1850-1900°F (1010-1040°C) is recommended to minimize hold time needed at austenitizing temperature.

Austenitize: 2100-2190° F (1150-1200°C)

Standard recommendation to achieve HRC 67-69 is 2150-2175°F (1175-1190°C).

Quench: Quench rapidly to below 1100°F (595°C), equalize, then air cool to hand warm, below 125°F (50°C). Salt or interrupted oil quenching usually gives the best heat treat response for high speed steels. A fast quench rate from hardening temperature to below 1100°F (595°C) is critical to achieve optimum heat treat response.

Temper: 1000°F (540°C) minimum. Triple or quadruple tempering required, hold 2 hr. minimum at temperature. Cool to room temperature between tempers.

Straightening: Best done warm 400°F minimum (205°C). Straightening after salt quenching and before cooling to below 400°F (205°C) is preferred.

Size Change During Hardening

Hardening Temperature	Tempering Temp.	HRC	Longitudinal Size Change
2175°F(1190C)	1025°F(550C)	68.5	+0.22%

Tempering Temp.	2100F (1150C)	2125F (1150C)	2150F (1175C)	2175F (1190C)	2190F (1200C)
As Quenched	68	68	67	66.5	66.5
1000°F(540°C)	67	67.5	68	68.5	69
1025°F(550°C)	66.5	67	67.5	68	68.5
1050°F(565°C)	65.5	66.5	67	67.5	68
1100°F(595°C)	63	64	65	66	66.5
1150°F(620°C)	59	60	61.5	63	64
1200°F(650°C)	53	55	57	59	60
Minimum Time at Aust. Temp.	10 min.	10 min.	5 min.	5 min.	3 min.
Minimum Number of Tempers	3	3	3	4	4

Heat Treat Response- (HRC) Oil or Salt Quench

